

Beta-Detected NQR in Zero Field with a Low Energy Beam of $^8\text{Li}^+$

Z. Salman ^{a,*} R.F. Kiefl ^b K.H. Chow ^c W.A. MacFarlane ^d S.R. Kreitzman ^a

D.J. Arseneau ^a S. Daviel ^a C.D.P. Levy ^a Y. Maeno ^e R. Poutissou ^a

^aTRIUMF, 4004 Wesbrook Mall, Vancouver, BC, V6T 2A3, Canada

^bDepartment of Physics and Astronomy, University of British Columbia, Vancouver, BC, V6T 1Z1, Canada

^cDepartment of Physics, University of Alberta, Edmonton, AB, T6G 2J1, Canada

^dDepartment of Chemistry, University of British Columbia, Vancouver, BC, V6T 1Z1, Canada

^eDepartment of Physics, Kyoto University, Kyoto 606-8502, Japan

Abstract

Beta-detected nuclear quadrupole resonances (β -NQR) at zero field are observed using a beam of low energy highly polarized radioactive $^8\text{Li}^+$. The resonances were detected in SrTiO_3 , Al_2O_3 and Sr_2RuO_4 single crystals by monitoring the beta-decay anisotropy as a function of a small audio frequency magnetic field. The resonances show clearly that ^8Li occupies one site with non-cubic symmetry in SrTiO_3 , two in Al_2O_3 and three sites in Sr_2RuO_4 . The resonance amplitude and width are surprisingly large compared to the values expected from transitions between the $|\pm 2\rangle \leftrightarrow |\pm 1\rangle$ spin states, indicating a significant mixing between the $|\pm m\rangle$ quadrupolar split levels.

Key words: Zero field, quadrupole resonance, β -NQR, β -NMR.

1. Introduction

Recently, we have constructed two spectrometers for beta-detected nuclear magnetic resonance [1] (β -NMR) and nuclear quadrupole resonance [2] (β -NQR), using a low energy highly polarized $^8\text{Li}^+$ beam. We report here on the first results obtained from the β -NQR spectrometer at zero applied magnetic field. The β -NQR spectra were obtained for ^8Li implanted into single crystals of SrTiO_3 , Al_2O_3 and Sr_2RuO_4 . The ability to perform measurements in zero applied field has many potential applications in studies of magnetism and supercon-

ductivity. It is also remarkable that the resonances are narrow (few kHz) and easily observed at acoustic frequencies.

This work is intended as an initial characterization of the spectra of ^8Li in SrTiO_3 , Al_2O_3 , and Sr_2RuO_4 . SrTiO_3 is probably the best-studied perovskite transition metal oxide. It is interesting for its prototypical soft mode structural phase transition (~ 105 K) [3], its ferroelectric properties [4,5], and as a high dielectric constant layer in heterostructures based on Si [6]. Both SrTiO_3 and Al_2O_3 are important substrate materials for thin films, and therefore it is important to understand the behavior of ^8Li in these substrates for future studies. Sr_2RuO_4 is an unconventional spin-triplet superconductor ($T_c = 1.5$ K) as demonstrated by

* Tel. +1 604 222 1047 x 6588, Fax: +1 604 222 1074, email: zaher@triumf.ca

NMR Knight shift measurements [7]. In its normal state it also exhibits a highly correlated metallic behavior which can be described as a quasi-two-dimensional Fermi liquid [8,9].

The experiment was performed at the TRIUMF ISAC facility in the new β -NQR spectrometer. In this experiment a highly polarized beam of ^8Li is implanted in the sample with energy of 30 keV. At this energy the average implantation depth is ~ 200 nm. A linearly polarized oscillating magnetic field B_1 is applied perpendicular to the initial nuclear spin polarization. A resonant loss of the nuclear beta decay asymmetry of ^8Li occurs when the frequency of the oscillating field ν matches the nuclear energy spin level splitting. A more detailed description of the β -NQR spectrometer and of the beta detected nuclear resonance technique used can be found in Ref.[2] and references therein. Once the development of this spectrometer is completed it will have the capability to reduce the beam energy to 100 eV, allowing for depth profiling measurements on a nm scale in zero applied magnetic field.

The Hamiltonian for the implanted ^8Li at zero field in the presence of an axially symmetric electric field gradient (EFG) is [10]

$$H_q = h\nu_q[I_z^2 - 2] \quad (1)$$

where $\nu_q = e^2qQ/8$, $eq = V_{zz}$ is the electric field gradient at the ^8Li site, and Q is the electric quadrupole moment of the nucleus. Therefore, when $q \neq 0$ even at zero magnetic field a splitting between the nuclear spin sub-levels $|m\rangle$ is present (see Fig. 1). In this case two resonance frequencies

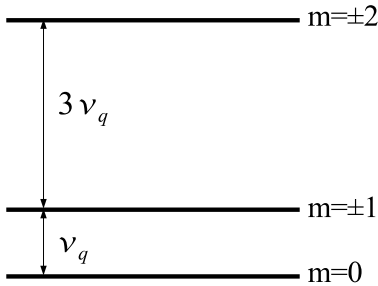


Fig. 1. The energy levels diagram for the Hamiltonian (1).

are possible, one at $\nu = \nu_q$ due to the transitions

$|\pm 1\rangle \leftrightarrow |0\rangle$, and another at $\nu = 3\nu_q$ due to $|\pm 2\rangle \leftrightarrow |\pm 1\rangle$ transitions.

2. Results

β -NQR spectra were collected on an epitaxially polished $\langle 100 \rangle$ single crystal of SrTiO_3 (Applied Crystal Technologies). We have established earlier that the ^8Li occupies the face centered site in SrTiO_3 [2,11], and therefore experiences a non-vanishing EFG. Indeed a large and sharp NQR resonance was observed at $3\nu_q = 228.81(2)$ kHz with width 1.7 kHz corresponding to the $|\pm 2\rangle \leftrightarrow |\pm 1\rangle$ transitions (see Fig. 2), whereas the resonance near ν_q was barely visible, indicating very low probability of ^8Li in the $|\pm 1\rangle$ spin states as expected from the high polarization of the ^8Li beam. Note the res-

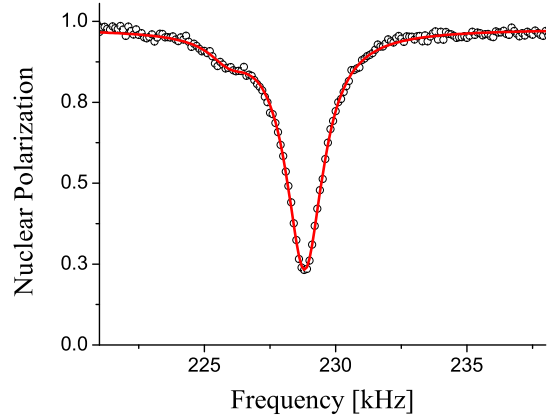


Fig. 2. The β -NQR spectrum in SrTiO_3 at room temperature and zero applied field

onance in Fig. 2 is slightly asymmetric. The solid curve is a fit assuming two overlapping lines. The smaller amplitude line occurs at a slightly lower frequency $\nu = 225.9(2)$ kHz and has a width of about 1.9(1) kHz which is similar to the higher frequency line at $\nu = 228.8$ kHz.

In Al_2O_3 (epitaxially polished, Honeywell) and Sr_2RuO_4 (freshly cleaved) the beta decay asymmetry was found to be zero when the ^8Li was implanted with its nuclear polarization perpendicular to the c-axis. However, when the sample was rotated by 45° significant asymmetry was

observed, a clear indication that the EFG experienced by the implanted ^8Li is along the c-axis in these crystals. In Al_2O_3 the spectrum (see Fig. 3) shows two distinct resonance lines at $\nu = 92.94(8)$ and $188.9(3)$ kHz, with widths of $15.1(3)$ and $22.5(9)$ kHz respectively. The two resonances are due to at least two inequivalent ^8Li sites. However,

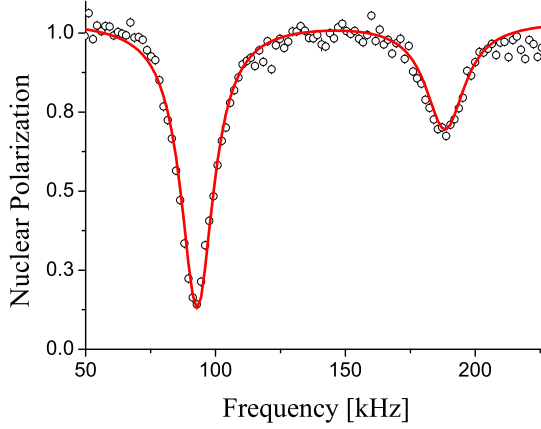


Fig. 3. The β -NQR spectrum in Al_2O_3 at room temperature and zero applied field.

note that the widths of the lines in Al_2O_3 are significantly larger than that observed in SrTiO_3 , likely due to a larger distribution of ν_q , which may be caused by multiple ^8Li sites with very similar values of ν_q . This may be expected considering the complexity of the lattice structure of Al_2O_3 .

The β -NQR spectrum in Sr_2RuO_4 is shown in Fig. 4 at room temperature and zero field, where three sharp and separated resonances are observed at $\nu = 7.72(4)$, $11.57(1)$ and $15.51(2)$ kHz, with corresponding width of $0.55(13)$, $1.28(3)$ and $0.83(7)$ kHz, indicating three well defined ^8Li lattice sites in this tetragonal material. The resonances here are even sharper than in SrTiO_3 , reflecting the high quality of this crystal.

In all three cases presented, the amplitude of the resonances are much larger than expected. The optical pumping method used to generate the nuclear polarization of the ^8Li beam produces polarization as high as $\sim 70\%$ along the measurement axis (z). This polarization can be defined as

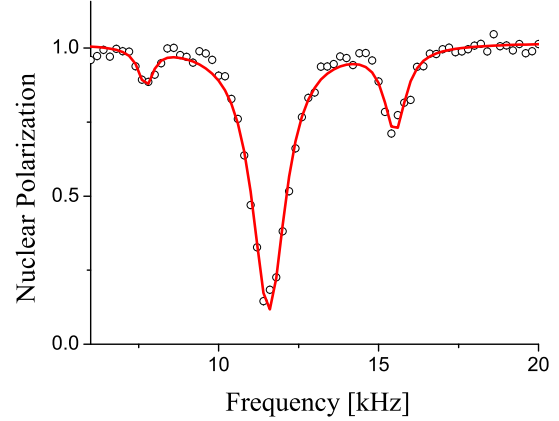


Fig. 4. The β -NQR spectrum in Sr_2RuO_4 at room temperature and zero applied field

$$P_z = \frac{1}{2} \sum_{m=-2}^{m=+2} p_m m \quad (2)$$

where p_m is the probability that the $|m\rangle$ state is occupied. Realistic values for these probabilities are

$$\{p_{+2}, p_{+1}, \dots, p_{-2}\} = \{0.65, 0.2, 0.15, 0, 0\}.$$

When the frequency of B_1 is $\nu = 3\nu_q$, and assuming sufficient power to saturate the transition, the probability that the $|+2\rangle$ or $|+1\rangle$ are occupied becomes equal. This implies that the polarization is reduced from its initial value, 0.75, to 0.6375 with probabilities $\{0.425, 0.425, 0.15, 0, 0\}$, i.e. 15% loss in the polarization or asymmetry. Our measurements show a considerably larger amplitude. This enhancement can be explained by an additional term in the Hamiltonian, which mixes the different sub-levels $|m\rangle$, and produces a larger effect by allowing transitions other than $|\pm 2\rangle \leftrightarrow |\pm 1\rangle$. Such a term can be produced by a small stray magnetic field perpendicular to the EFG axis, or by non-axial terms in the EFG. In the case of SrTiO_3 we concluded that the non-axial terms in the EFG are responsible for this enhancement [2]. However, more measurements are required on Al_2O_3 and Sr_2RuO_4 to identify the origin of the additional interaction responsible for the amplitude enhancement.

Interestingly, in addition to the large amplitudes, the sum of the amplitudes in the case of

Al_2O_3 and Sr_2RuO_4 is larger than 1, as seen in Fig. 3 and 4. This is only possible if ^8Li is diffusing between inequivalent sites. When the diffusion rate is higher than the ^8Li decay rate, it would be possible for a ^8Li particle which is initially *off resonance* to move to an *on resonance* site, thus increasing the measured amplitude. This will be verified by cooling the sample and measuring the β -NQR spectra as a function of temperature, where one expects the diffusion rate to slow down, and consequently the sum of amplitudes to drop below 1.

3. Summary and Conclusion

We have demonstrated that it is possible to carry out β detected nuclear quadrupole resonance using a beam of low energy highly polarized $^8\text{Li}^+$. Clear β -NQRs were observed in SrTiO_3 , Al_2O_3 , and Sr_2RuO_4 indicating that the implanted Li adopts well defined crystalline lattice sites. In contrast to μ^+ , the quadrupole resonances provide a means of identifying the ^8Li site.

There is evidence for small terms in spin Hamiltonian which lead to mixing of the $|\pm m\rangle$ states and a dramatic enhancement of the amplitude of the resonances at $3\nu_q$. The ability to perform μSR in zero field has been used extensively in studies of magnetism and superconductors. We anticipate similar applications are possible with β -NQR in studies of ultra-thin films and interfaces. For example in superconductors it could be used to measure the absolute value of the London penetration depth or to search for states with broken time reversal symmetry. In semiconductors or ionic compounds it can be used to study the diffusion and electronic structure of isolated Li in reduced geometries.

We also thank Laura Greene for providing the SrTiO_3 sample.

References

- [1] G. D. Morris W. A. MacFarlane K. H. Chow Z. Salman D. J. Arseneau S. Daviel A. Hatakeyama S. R. Kreitzman C. D. P. Levy R. Poutissou R. H. Heffner J. E. Elenewski L. H. Greene and R. F. Kiefl. *Phys. Rev. Lett.*, 93:157601, 2004.
- [2] Z. Salman E.P. Reynard W.A. MacFarlane K.H. Chow J. Chakhalian S.R. Kreitzman S. Daviel C.D.P. Levy R. Poutissou and R.F. Kiefl. *Phys. Rev. B*, 70:104404, 2004.
- [3] R.A. Cowley. *Phil. Trans. R. Soc. London A*, 354:2799, 1996.
- [4] J.G. Bednorz and K.A. Müller. *Phys. Rev. Lett.*, 52:2289, 1984.
- [5] M. Itoh R. Wang Y. Inaguma T. Yamaguchi Y.J. Shan and T. Nakamura. *Phys. Rev. Lett.*, 82:3540, 1999.
- [6] R.A. McKee F.J. Walker and M.F. Chisholm. *Phys. Rev. Lett.*, 81:3014, 1998.
- [7] K. Ishida H. Mukuda Y. Kitaoka K. Asayama Z.Q. Mao Y. Mori and Y. Maeno. *Nature*, 396:658, 1998.
- [8] A.P. Mackenzie S.R. Julian A.J. Diver G.J. McMullan M.P. Ray G.G. Lonzarich Y. Maeno S. Nishizaki and T. Fujita. *Phys. Rev. Lett.*, 76:3786, 1996.
- [9] Y. Maeno et. al. *J. Phys. Soc. Jpn.*, 66:1405, 1997.
- [10] C.P. Slichter. *Principles of Magnetic Resonance*. Springer-Verlag, New York, third edition, 1990.
- [11] W. A. MacFarlane G. D. Morris K. H. Chow R. A. Baartman S. Daviel S. R. Dunsiger A. Hatakeyama S. R. Kreitzman C. D. P. Levy R. I. Miller K. M. Nichol R. Poutissou E. Dumont L. H. Greene and R. F. Kiefl. *Physica B*, 326:209, 2003.

Acknowledgements This work was supported by the CIAR, NSERC and TRIUMF. We thank Rahim Abasalti and Bassam Hitti for technical